

Point-contact spectroscopy on URu₂Si₂

J.G. Rodrigo^a, F. Guinea^b, S. Vieira^a, and F.G. Aliev^c.

Instituto Universitario de Ciencia de Materiales “Nicolás Cabrera”

^a*Laboratorio de Bajas Temperaturas. Departamento de Física de la Materia Condensada.
Universidad Autónoma de Madrid. 28049 Madrid, Spain.*

^b*Instituto de Ciencia de Materiales, CSIC. 28049 Madrid, Spain.*

^c*Laboratorium voor Vaste Stoffysica en Magnetisme. Katholieke Universiteit Leuven.
Celestijnenlaan 200D, B3001 Leuven, Belgium.*

(February 1, 2008)

Tunnel and point contact experiments have been made in a URu₂Si₂ single crystal along the *c*-axis. The experiments were performed changing temperature and contact size in a low temperature scanning tunneling microscope. A resonance develops at the Fermi level at $T \sim 60$ K. This resonance splits and becomes asymmetric when the 17.5 K phase transition is crossed. These results are consistent with the existence of Kondo like bound states of the U⁴⁺ ionic configurations and the conduction electrons. Below the transition, these configurations are split by the development of quadrupolar ordering. The peak separation can be interpreted as a direct measurement of the order parameter. Measurements on a polycrystalline UAu₂Si₂ sample are also reported, with a comparative study of the behavior of both materials.

A large effort has been made in the last years to understand the low temperature behaviour of uranium based ternary intermetallic alloys. Magnetic and superconducting phase transitions have been found on UT₂Si₂ compounds (T refers to a transition element), which have been the subject of intensive experimental and theoretical studies. A comprehensive explanation of the behavior of these materials is, however, still lacking. One the most studied compound of this family is URu₂Si₂. Among other remarkable features, this compound exhibits antiferromagnetism below 17.5K and superconductivity below 1K. The nature of the pairing, and the origin of the transition at 17.5K are not completely understood. Different experiments including specific heat, thermal expansion, magnetic susceptibility, resistivity, inelastic neutron scattering, and tunnel and point contact spectroscopies, have been made, with special emphasis in the search of an explanation of the 17.5 K transition. The fact that the measured magnetic moment per uranium atom in the magnetically ordered phase is $0.04 \mu_B$, is in contrast with the measured moments per uranium atom, 1.6 - $3.0 \mu_B$, for the other UT₂Si₂ alloys on which neutron scattering experiments have been performed.

As pointed in ref. [1], it is difficult to identify such a small magnetic moment with the order parameter of an antiferromagnetic phase transition with Néel temperature of 17.5K, if we take account the large anomalies observed in several quantities at this temperature. Based on these experimental facts, Ramirez *et.al.* [2] proposed several years ago that the order parameter is not the tiny magnetic moment [3]. This is a secondary effect originated because the fundamental order parameter breaks time-reversal symmetry, which allows a linear coupling to the staggered magnetic order, inducing the measured magnetic moment (see, however [4], for an alternative explanation). Following this idea, a model based on quadrupolar ordering of localized *f* electrons has been developed in ref. [1], which reproduces semiquantitatively the magnetic properties of URu₂Si₂. The model assumes an effective coupling between the U⁴⁺ configurations in different U atoms, which is presumably induced by the conduction electrons. The level ordering which best fits the experimental results has three singlets at low energies, while the doublets lie at higher energies. This model has been generalized in [5], by also including the magnetic configurations of the U³⁺ and U⁵⁺ charge states.

In the following, we will try to gain information on the U ionic configurations, and their coupling to the conduction electrons, by means of tunnel and point contact spectroscopy. Electron tunneling and point-contact spectroscopies have been useful tools to study electronic properties of several UT₂Si₂. Several experiments have been made during the last years [6–9], although a consistent interpretation in terms of the hybridization of the U configurations and the conduction electrons is still lacking.

In previous works we have used a scanning tunneling microscope (STM), which we can cover temperatures ranging from 2 K up to 300 K operating inside a ⁴He cryostat [10], to study the conductance behaviour of nanoscopic size junctions between different materials. The electrodes are displaced, in a controlled way, from a vacuum tunneling regime to point contact [11]. Similar procedures were followed in the present experiments. The URu₂Si₂ samples were thin slices cleaved perpendicular to the *c*-axis from a high quality single crystal, which has been characterized by measuring magnetic susceptibility [12] and heat capacity. The specific heat showed a sharp peak (width less than 0.5 K) near 17 K. The sample also shows a superconducting transition at $T_c \simeq 1.2$ K, with a transition width of

~ 0.1 K. Noble metals, platinum and gold, were used as tip counterelectrodes. The experiments were performed by changing the temperature, between 4.2 K and 40 K, and changing the area of the contact. We compare these results with the ones obtained in an UAu_2Si_2 polycrystalline sample, which presents ferromagnetic ordering near 17 K, and with junctions formed with two URu_2Si_2 electrodes.

At a selected spot on the sample current vs. voltage, $I(V)$, and current vs. tip-to-sample distance, $I(d)$, curves can be taken. Typically, these curves are taken in 100 ms with 1024 data points. Differential conductance curves, $dI/dV(V)$, are obtained by numerical derivation of the $I(V)$ data. Varying the z-piezo voltage we can cover vacuum tunneling and clean contact regimes with resistance ranging from several $\text{M}\Omega$ down to a few ohms.

Every experimental round starts at 4.2 K with topographical and spectroscopical explorations. $I(d)$ curves are taken to check the cleanliness of the contact [13]. Then, series of $I(V)$ curves are taken for different junction resistances. The main feature in the conductance curves is a central hump at zero bias, which presents two asymmetric peaks respect to bias voltage (Fig.1 (A)).

Once we have reached the contact regime, we study the evolution of different features in the $dI/dV(V)$ curves as a function of temperature in repeated cycles up to 40 K. These features are the position of conductance peaks, Δ^+ and Δ^- , its separation Δ_{pp} , and the normal conductance of the contact, G_N , (i.e. the value of dI/dV at high voltage, ~ 100 mV, because no heating effects are detected).

In Fig. 1(B) we present a series of conductance curves corresponding to one thermal cycle. We observe that, as the temperature increases from 4.2 K the peaks move to zero voltage, they evolve into a single hump at about 20 K, then this hump broadens and decreases its height until it almost disappears at higher temperatures. This evolution can be extrapolated, and we find the onset of this resonance at Fermi level at $T \simeq 60$ K.

The insets in Fig. 1(B) show the evolution of the parameters mentioned above. In inset (a) we present the evolution of the conductance peaks: for low temperatures Δ^+ is smaller than Δ^- , which can be extrapolated to $\Delta_0^+ \simeq 6$ meV and $\Delta_0^- \simeq 8$ meV at $T = 0$ K, and at higher temperatures they decrease uniformly, having $\Delta^\pm = 0$ at $T_N \simeq 22$ K. From these data, we consider $T_N \simeq 22$ K as the transition temperature to the antiferromagnetic state in our experiment.

Inset (b) shows the evolution of G_N : an increase of G_N (and therefore an increase of the electronic density of states) respect to the value at low temperature takes place when $T > T_N$, as has been previously stated by other authors from specific heat measurements [14]. We observe this effect both in series taken in constant current mode (there is a clear change in the feedback signal when T_N is crossed), and in series taken with fixed voltage applied to the piezo.

There is one question concerning the *high* value that we obtain for T_N , compared with the value commonly found in the literature ($T_N \simeq 17$ K). In our experiments we are doing point-contact spectroscopy using a STM, with reasonably clean contacts, whose radii are about 50 Å. In these conditions, in similar STM experiments [15], it has been shown that the pressure at the contact is of the order of 1 GPa (~ 10 kbar). These values can be reached because the fact that the STM tip is small. Resistivity measurements in URu_2Si_2 have shown an increase of T_N with pressure [16]. The behaviour of T_N vs P is in good quantitative agreement with our observation of $T_N \simeq 22$ K for $P \sim 10$ kbar. This effect can also be noticed in other spectroscopic works on URu_2Si_2 . In point-contact measurements using an STM [8], the double peak in dI/dV develops at temperatures similar to those in our experiment. When standard point-contact is used [7,9], involving larger contact areas than in STM experiments, and thus less pressure at the contact, the double peak develops at temperatures closer to $T_N(P = 1 \text{ bar}) \simeq 17$ K.

If we pay attention to the evolution of $dI/dV(V)$ series at fixed temperature and varying the contact resistance (Fig.1(A)), we observe that the double peaked central structure increases its height as we attain higher conductance values (i.e., larger size of the contact). This is a common situation when inelastic scattering processes are involved in point-contact spectroscopy measurements [17]. In this case, the larger the ratio a/l (with a radius of the contact, and l inelastic electron mean free path), the larger will be the information about inelastic processes that appears in the conductance spectra. This is usually observed in measurements of the phonon structure in normal metals.

The double peak structure found experimentally can be well approximated by two (or three, see below) lorentzians whose separation is proportional to $\sqrt{T_N - T}$, and whose average position deviates from the Fermi level as $T_N - T$. A simulation of the evolution of the conductance with temperature is shown in inset (c) of Fig.1. We have used two states (lorentzians) with the same initial width (12 mV) that increases like T^2 , and with heights ratio of 1.33. Temperature varies from 4 K to 22 K.

In Fig. 2(A) we present the evolution of dI/dV vs. T for symmetric URu_2Si_2 contacts [18]. In this case the conductance peaks are always symmetric, and their separation vs. temperature is shown in inset (a). We also observe a sharp change in $G_N(T)$ at T_N : $G_N(T)$ is even ten times larger for $T > T_N$ than for $T < T_N$ (inset (b)). This high increase of G_N would be in agreement with the fact that now both electrodes have an increase of the electronic density of states for $T > T_N$.

We have repeated these experiments with UAu_2Si_2 in order to check differences and similarities with URu_2Si_2 .

UAu₂Si₂ presents a phase transition at ~ 17 K at zero pressure leading to a ferromagnetic state, as it is observed in other compounds of this family, like UPt₂Si₂. Conductance curves measured at 4.2 K present a single hump at zero bias, symmetrical respect to voltage, which broadens and decreases its height continuously, becoming almost negligible at 25 K (Fig.2(B)). In this case there is no sharp change in $G_N(T)$ during the thermal cycles. This fact supports the previous discussion about the evolution of $G_N(T)$ in URu₂Si₂, because, to our knowledge, there is no evidence in the literature about a loss of part of the Fermi surface in these heavy fermion systems due to the phase transition.

We now interpret the resonances in URu₂Si₂ as arising from bound states of conduction electrons and configurations of U⁴⁺, in analogy to the “Kondo peak” in spin 1/2 Kondo systems. We analyze the evolution of the U⁴⁺ configurations within the scheme proposed in [1], which is consistent with magnetic susceptibility and specific heat experiments. A refinement of this analysis is presented in ref. [5]. The scheme proposed in ref. [1] analyses the low energy properties of URu₂Si₂ in terms of the configurations of U⁴⁺ only. It is suggested in ref. [5] that the observed magnetization below T_N in this material can be due to an admixture of spin 1/2 configurations of U³⁺ and U⁵⁺ in a broken spin symmetry state. This mixing is assumed to be small, in order to account for the small magnetic moment below the transition temperature. In the following, we will interpret the present experiments in terms of the low energy configurations of U⁴⁺ only. We do not expect significant changes due to the introduction of the U³⁺ and U⁵⁺ configurations. Note that, as far as the effect of the phase transition on the configurations of U⁴⁺ is concerned, refs. [1] and [5] are not contradictory.

According to ref. [1], the low energy properties of the U ions is dominated by three low lying singlets. Hybridization with the conduction band electrons are expected to induce transitions between these states, in a similar manner to the quadrupolar Kondo fluctuations proposed for UBe₁₃ [19]. In the present case, however, orthogonal symmetry breaks the degeneracy of the two lowest lying singlets (Γ_{t2} and Γ_{t1}^1 , in the notation of ref. [1]).

The electron spectroscopy experiments show the development of a symmetric resonance at zero voltage at low temperatures. We identify this resonance as a Kondo-like peak [20]. It arises from the scattering between the two lowest lying U⁴⁺ configurations, induced by the conduction electrons. The associated Kondo temperature is $T_K \sim 60$ K. The fact that the resonance is nearly symmetric around zero voltage implies that virtual fluctuations into U³⁺ and U⁵⁺ charge states are equally likely. The splitting between the low lying U⁴⁺ configurations proposed in ref. [1] is ~ 9 meV. As they are of the order, or less, than T_K , they cannot be resolved.

It is proposed in ref. [1] that, below the transition, an additional quadrupolar field acts on the U⁴⁺ ions. This field mixes two low lying configurations (Γ_{t3} and Γ_{t1}^1), and increases their separation in energies. In the presence of these effects, the tunneling density of states should resemble that of the Kondo model in a magnetic field [21], which shows two separate resonances. Within this interpretation, the splitting between the two peaks that we find below T_N should be directly proportional to the order parameter, and scale as $\sqrt{T_N - T}$. This behavior is, indeed, consistent with the results reported here as shown in the good simulation presented in Fig.1 (B), where the experimental curves have been modelled by two lorentzians whose separation scales as $\sqrt{T_N - T}$, and different heights. The inclusion of a third low energy resonance which is not changed by the transition (Γ_{t2}) does not affect the quality of the result. An alternative proposal, discussed in the literature, is the formation of an antiferromagnetic gap at the Fermi surface, associated to the magnetic order parameter. We find this interpretation less plausible than the one given above as i) the AF order parameter is very small, and ii) it implies the existence of a fully coherent heavy fermion band, with significant nesting at the Fermi surface.

We finally address the question of the asymmetry between the two peaks which arises at low temperatures. This asymmetry cannot be explained by the opening of a gap at the Fermi level in an otherwise symmetric band. It does not arise in a Kondo system in a magnetic field, where the two spin states are split symmetrically. In the present case, a quadrupolar field mixes more than the two configurations considered so far. The order parameter proposed in ref. [1], $J_x^2 - J_y^2$, hybridizes the two previously mentioned states, Γ_{t3} and Γ_{t1}^1 with Γ_{t1}^2 , which lies higher in energy. This additional hybridization also increases with the order parameter, $\sim (T_N - T)^{1/2}$. The high energy configuration repels the two low lying ones towards lower energies. The average shift in Γ_{t3} and Γ_{t1}^1 goes as the square of the order parameter, $\sim T_N - T$. This displacement of the mean position is consistent with the experiments, as also shown in Fig.1 (B).

Note, finally, that the splitting induced by a quadrupolar crystal field can be much larger than typical spin splittings due to magnetic transitions. We think that this is the reason for the unobservability of a splitting of the Kondo resonance in UAu₂Si₂ below the ferromagnetic transition.

In summary, we have presented a series of electron spectroscopy experiments using an STM, with the aim of investigating the 17.5 K phase transition in URu₂Si₂. Our experimental conductance series, both for different contact resistances at fixed temperature, and for different temperatures keeping constant the resistance of the contact, suggest

that the peaked features in the spectra are consistent with the existence of “Kondo like” resonances built up from the different U^{4+} configurations and the conduction electrons. Below the transition temperature, these resonances are split by the appearance of quadrupolar ordering. In addition, the ordering induces an asymmetry in the density of states, associated to the large number of ionic configurations affected by the transition.


We would like to thank R. Villar and C. Sirvent for their suggestions and help, and D. Hinks, Argonne National Laboratory, Illinois, USA, for sample preparation. This work has been supported by grants MAT94-0982, MAT95-1542, and PB94-0382 (DGICYT).

-
- [1] P. Santini and G. Amoretti, Phys. Rev. Lett. **73**, 1027 (1994).
 - [2] A. P. Ramirez, P. Coleman, P. Chandra, E. Brück, A. A. Menovsky, Z. Fisk and E. Bucher, Phys. Rev. Lett. **68**, 2680 (1992).
 - [3] C. Broholm, H. Lin, P. T. Matthews, T. E. Mason, W. J. L. Buyers, M. F. Collins, A. A. Menovsky, J. A. Mydosh and J. K. Kjems, Phys. Rev. B **43**, 12809 (1991).
 - [4] M. B. Walker, W. J. L. Buyers, Z. Tun, W. Que, A. A. Menovsky and J. D. Garret, Phys. Rev. Lett. **71**, 2630 (1993).
 - [5] V. Barzykin and L. P. Gorkov, Phys. Rev. Lett. **74**, 4301 (1995).
 - [6] F.G. Aliev, V. Kovachik, V.V. Moshchalkov, V.V. Pryadun, N.E. Alekseevskii, A.V. Mitin, N. Agraït, S. Vieira, and R. Villar, J. Low Temp. Physics **85** (5/6), 359 (1991).
 - [7] A. Nowack, Yu. G. Naidyuk, P. N. Chobov, I. K. Yanson, and A. Menovsky, Z. Phys. B - Condensed Matter **88**, 295 (1992). Yu. G. Naidyuk, H. v. Löhneysen, G. Goll, I. K. Yanson and A. A. Menovsky, Europhys. Lett. **33**, 557 (1996).
 - [8] K. Hasselbach, J. R. Kirtley, and P. Lejay, Phys. Rev. B **46**, 5826 (1992).
 - [9] R. Escudero, F. Morales, and P. Lejay, Phys. Rev. B **49**, 15271 (1994).
 - [10] J.G. Rodrigo, Ph.D. Thesis. Departamento de Física de la Materia Condensada, Universidad Autónoma de Madrid, Spain (1994).
 - [11] N. Agraït, J.G. Rodrigo, and S. Vieira, Phys. Rev. B **46**, 5814 (1992). J.G. Rodrigo, N. Agraït, and S. Vieira, Phys. Rev. B **50**, 374 (1994). J.G. Rodrigo, N. Agraït, C. Sirvent, and S. Vieira, Phys. Rev. B **50**, 12788 (1994).
 - [12] F.G. Aliev, S. Vieira, R. Villar, and J.L. Martínez, Pisma Zh. Exper. Teor. Fiz. **61** (3), 201 (1995) [JETP Lett. **61**, 205 (1995)].
 - [13] J.K. Gimzewski and R. Möller, Phys. Rev. B **36**, 1284 (1987).
 - [14] M. B. Maple, J. W. Chen, Y. Dalichaouch, T. Kohara, C. Rossel, and M. S. Torikachvili and M. W. McElfresh, and J. D. Thompson, Phys. Rev. Lett. **56**, 185 (1986).
 - [15] G. Rubio, N. Agraït, and S. Vieira, Phys. Rev. Lett. **76**, 2302 (1995).
 - [16] M. W. McElfresh, J. D. Thompson, J. O. Willis, M. B. Maple, T. Kohara, and M. S. Torikachvili, Phys. Rev. B **35**, 43 (1987).
 - [17] A.M. Duif, A.G.M. Jansen, and P. Wyder, J. Magn. Magn. Mat. **63 & 64**, 664 (1987). A.M. Duif, A.G.M. Jansen, and P. Wyder, J.Phys.: Condens. Matter **1**, 3157 (1989). A.G.M. Jansen, A.P. van Gelder, and P. Wyder, J.Phys. C: Solid St. Phys. **13**, 6073 (1980).
 - [18] In the experimental conductance curves (see Fig.3), we observe a depression of the conductance at both sides of the central peak structure, before to reach a constant value at high voltage. This is the expected result for the conductance corresponding to a density of states with Lorentzian spectral functions (see S. Q. Murphy, J. P. Eisenstein, L. N. Pfeiffer, and K. W. West, Phys. Rev. B **52**, 14825 (1995)).
 - [19] D. L. Cox, Phys. Rev. Lett. **59**, 1240 (1987).
 - [20] T. K. Ng and P. A. Lee, Phys. Rev. Lett. **61**, 1768 (1988).
 - [21] Y. Meir, N. S. Wingreen and P. A. Lee, Phys. Rev. Lett. **66**, 3048 (1991).

FIG. 1. A) Normalized conductance spectra taken at 4.2 K with different contact resistance for Pt - URu_2Si_2 contacts. R_N values are: 15, 20, 25, 40, 50, 105 and 110 Ω (from top to bottom). B) Normalized conductance spectra of a Pt - URu_2Si_2 contact, with temperature varied from 4.2 K to 25 K. Insets: (a) evolution of the peaks positions with temperature. Lines are fits to the dependences proposed in the text; (b) variation of the conductance with temperature; (c) simulation of the evolution of the URu_2Si_2 conductance with temperature using two lorentzian functions.

FIG. 2. A) Normalized conductance spectra obtained in the range $4.2 \text{ K} \leq T \leq 30.5 \text{ K}$ for a URu_2Si_2 - URu_2Si_2 contact. Insets: evolution of peaks separation (a) and normal conductance (b) with temperature. B) Normalized conductance spectra obtained in the temperature range $4.2 \text{ K} \leq T \leq 25 \text{ K}$ for a Pt - UAu_2Si_2 contact with $R_N \sim 50 \Omega$.

Fig.1

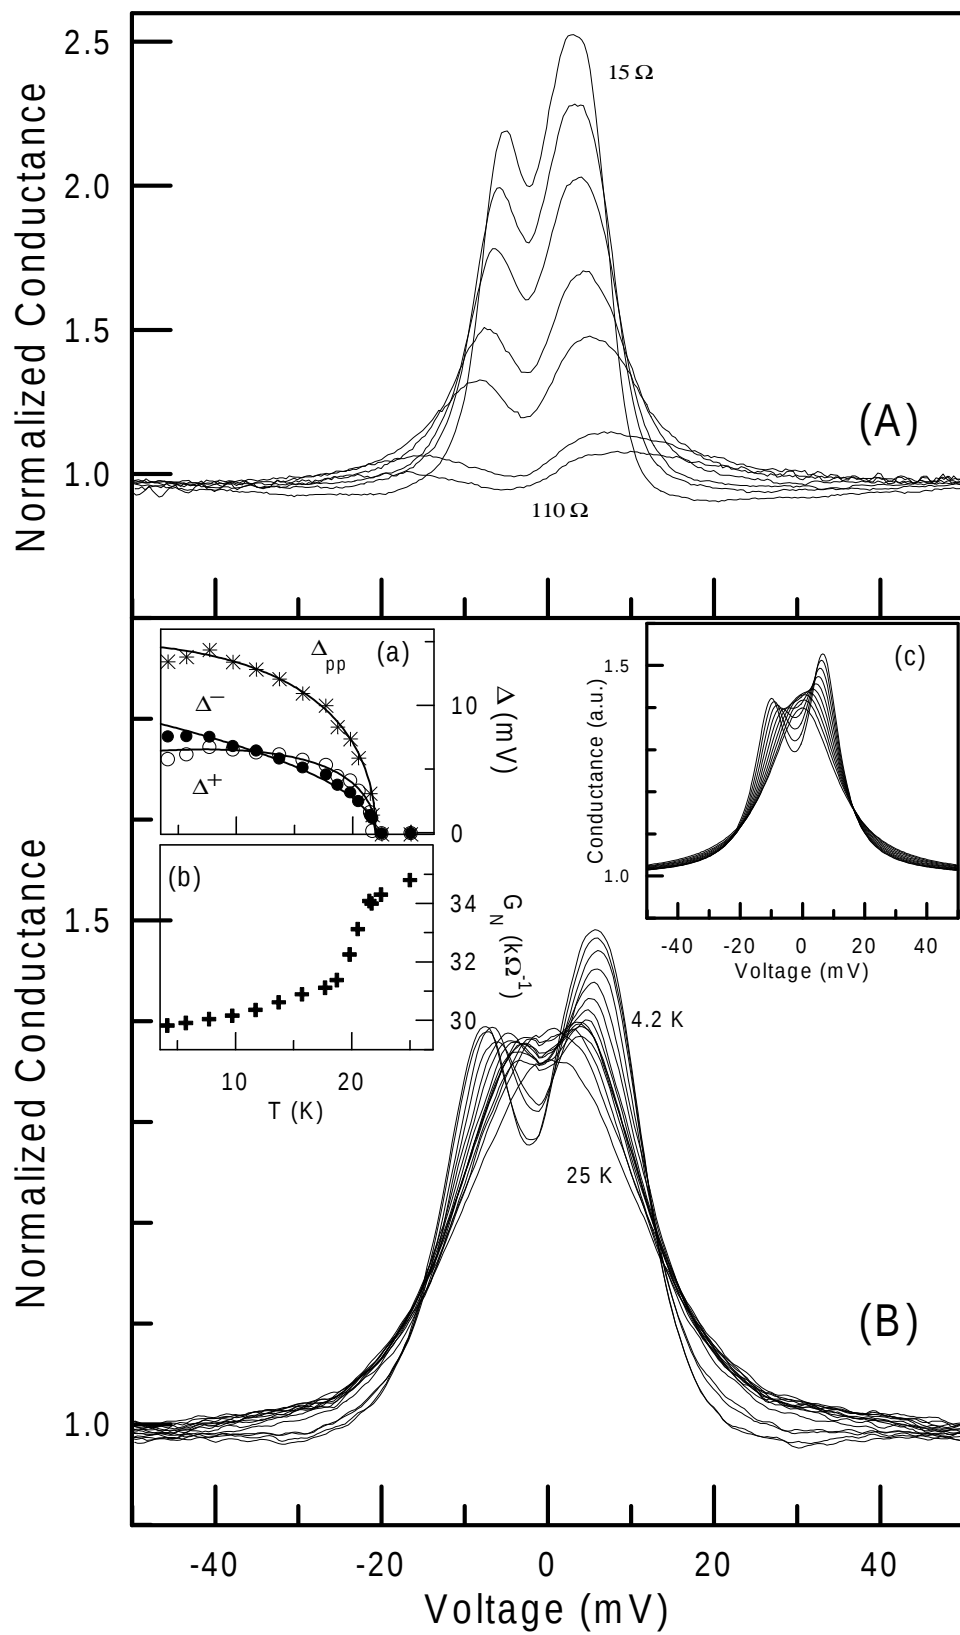

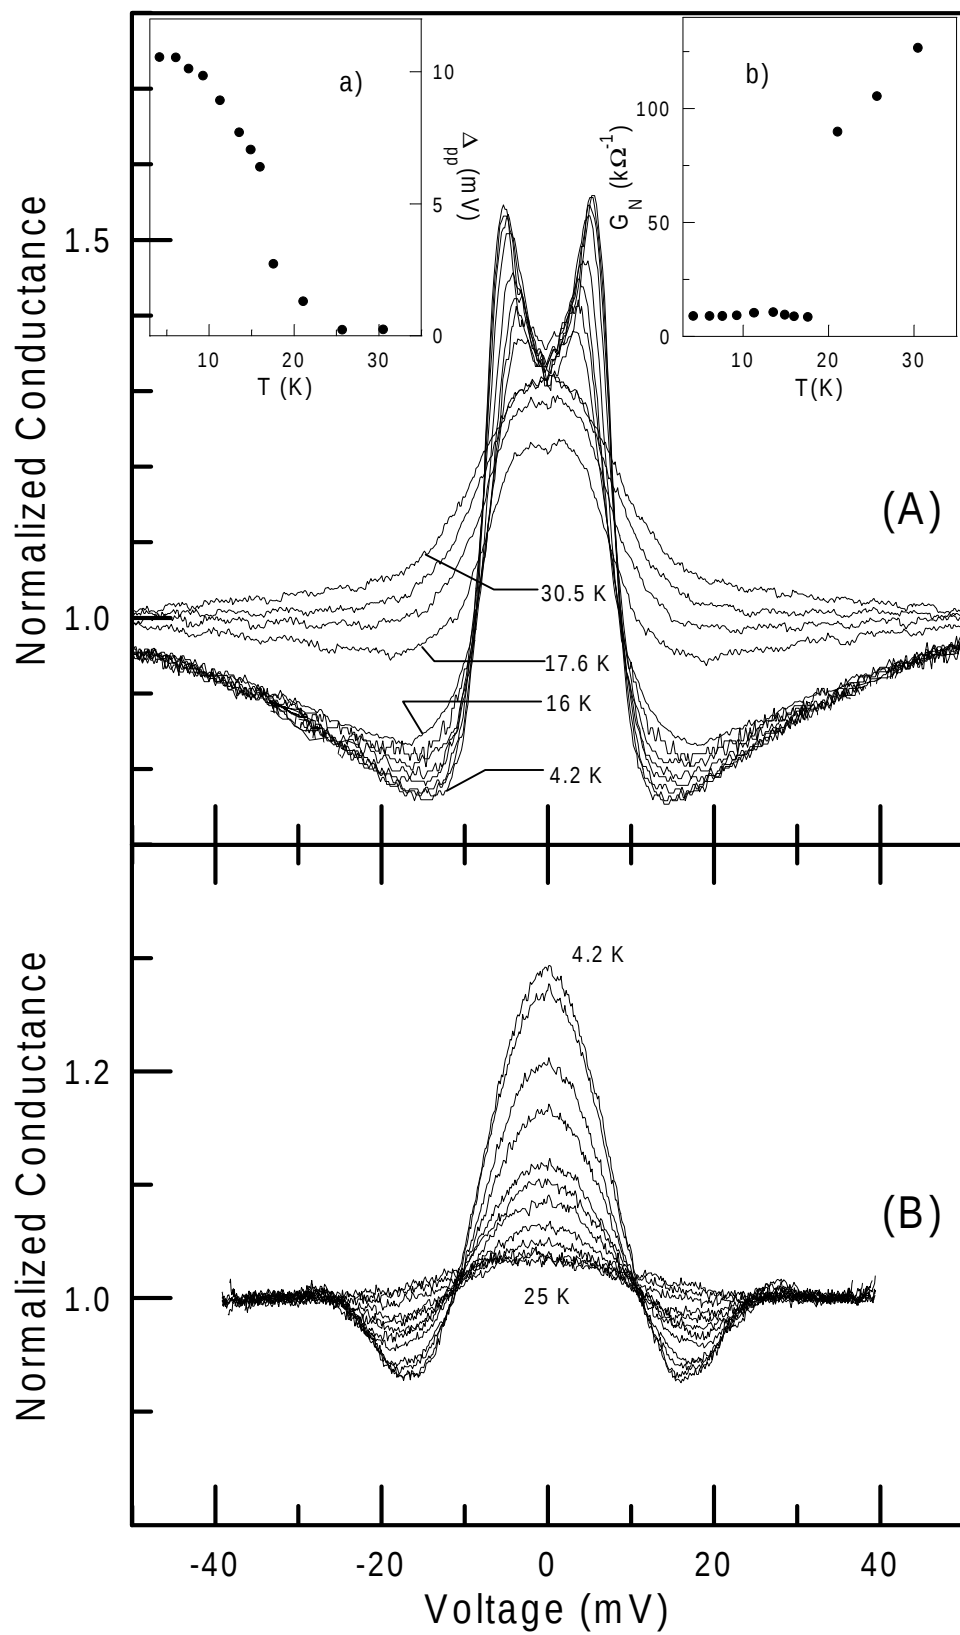


Fig.2